

LOCTITE®



LOCTITE® 3D IND403™

General Purpose
Black, Natural

LOCTITE®

Henkel Corporation
loctite3d@henkel.com



LOCTITE®

IND403™

GENERAL PURPOSE



LOCTITE 3D IND403™

LOCTITE 3D IND403 is a high temperature resistance material that allows the production of parts with high surface quality and outstanding dimensional accuracy.

LOCTITE 3D IND403 is ideal for tooling production for processes such as silicone casting, low pressure molding and open mold PU molding. The material can withstand mechanical stresses while maintaining dimensional stability for multiple cycles, for fast product development and rapid process iteration.



Benefits:

- High heat deflection temperature, HDT 80°C
- Tough with good dimensional stability
- Good surface finish



Ideal for:

- Tooling and molds
- Interior applications in automotive



Markets:



Industry



Automotive



Consumer Goods

Tensile Stress at Break (MPa)

70

Young's Modulus (MPa)

2,600

Elongation at Break (%)

10

IZOD Impact (Noched, J/m)

27

HDT at 0.455 (MPa)

80

**Values shown are linked to LOCTITE IND403 Black as reference, please refer to the specific mechanical properties for each of the colors shown in this document*





IND403™ GENERAL PURPOSE BLACK



PROPERTIES

Mechanical Properties	Measure	Method	Green	Post Processed
Young's Modulus	MPa	ASTM D638	1680 – 1880 ^[1]	2540 – 2600 ^[2]
Tensile Stress at Yield	MPa	ASTM D638	37 – 43 ^[1]	70 – 74 ^[2]
Elongation at Yield	%	ASTM D638	3 – 4 ^[1]	4 – 5 ^[2]
Tensile Stress at Break	MPa	ASTM D638	29 – 34 ^[1]	64 – 70 ^[2]
Elongation at Break	%	ASTM D638	11 – 31 ^[1]	7 – 13 ^[2]
Poisson's Ratio	-	ASTM D638	-	0.32 – 0.36 ^[9]
Flexural Modulus	MPa	ASTM D790	1840 – 1920 ^[3]	2585 – 2720 ^[4]
Flexural Stress at Break	MPa	ASTM D790	-	-
Flexural Elongation at Break	%	ASTM D790	> 5 ^[3]	> 5 ^[4]
IZOD Impact (Notched)	J/m	ASTM D256	-	22 – 32 ^[5]
Shore Hardness (3s)	D	ASTM D2240	76 ^[6]	78 ^[7]
Other Properties				
HDT at 0.455 MPa	°C	ASTM D648	-	81 – 83 ^[13]
HDT at 1.82 MPa	°C	ASTM D648	-	64 – 66 ^[14]
Water absorption (24h)	%	ASTM D570	-	1.8 – 1.9 ^[9,1,9]
Water absorption (48h)	%	ASTM D570	-	2.5 – 2.6 ^[9]
Water absorption (72h)	%	ASTM D570	-	3.0 – 4.3 ^[9, 9.1]
Water absorption (168h)	%	ASTM D570	-	4.6 – 5.0 ^[9, 9.1]
Solid Density	g/cm ³	ASTM D792	1.17 ^[8]	1.20 ^[8]
Thermal Conductivity	mW/(m·K)	ASTM D5930	-	220 – 224 ^[15]
Heat Capacity	J/(g·K)	ASTM D5930	-	1.38 – 1.54 ^[15]

Test parameters:

All specimen are printed unless otherwise noted. All specimen were in ambient lab conditions at 19-23°C / 40-60% RH for at least 24 hours. ASTM Methods: D638 Type IV, 5mm/min; D790-B 1.3 mm/min; D256 Notched IZOD (Machine Notched) 6 mm x 12 mm; D2240 Type "D" (3, 5 seconds); D648 127 mm x 13 mm x 6.8 mm; D570 3.2 mm x 51 mm Disc 24hr@ 25°C; D792 solid 8 mm x 10 mm Disc; D5930 80 mm x 40 mm x 10 mm; E831 80 mm x 40 mm x 10 mm; D7867@ 25°C (77°F); D1475; D149 50 mm x 3 mm disc; D257 110 mm x 110 mm x 5 mm; D150 70 mm x 70 mm x 1.2 mm.

*The biological assessment has been performed based on the in vitro method according to ISO10993-23

Internal Data Sources:

[1] FOR22924 [2] FOR22926 [3] FOR16923 [4] FOR20444 [5] FOR16913 [6] FOR16912 [7] FOR16911 [8] FOR16928 [9] FOR593799 [9.1] FOR51810 [13] FOR19730 [14] FOR16920 [15] FOR26106 [16] FOR751204





IND403™ GENERAL PURPOSE BLACK



PROPERTIES

Mechanical Properties	Measure	Method	Green	Post Processed
CTE (< T _{G1})	μm/(m·K)	ASTM E831	-	72 – 76 [10]
CTE (> T _{G2})	μm/(m·K)	ASTM E831	-	134 – 146 [10]
T _{G1} (Primary)	°C	ASTM E831	-	50 – 62 [10]
T _{G2} (Secondary)	°C	ASTM E831	-	92 – 94 [10]
Liquid Properties				
Viscosity at 25°C (77°F)	cP	ASTM D7867	-	100 – 200 [11]
Liquid Density	g/cm ³	ASTM D1475	-	1.08 [12]
Electrical Properties				
Dielectric Strength	kV/mm	ASTM D149	-	24 - 26 [16]
Volume Resistivity	Ω·cm	ASTM D257	-	2.5·10 ¹⁵ [17]
Surface Resistivity	Ω	ASTM D257	-	1.9·10 ¹⁵ [17]
AC Relative Permittivity (Dielectric Constant)				
at 50 Hz	none	ASTM D150	-	4.7 [18]
at 1 kHz	none	ASTM D150	-	4.5 [19]
at 1 MHz	none	ASTM D150	-	4.0 [20]
AC Loss Characteristic (Dissipation Factor)				
at 50 Hz	none	ASTM D150	-	0.014 [18]
at 1 kHz	none	ASTM D150	-	0.014 [19]
at 1 MHz	none	ASTM D150	-	0.040 [20]

Test parameters:

All specimen are printed unless otherwise noted. All specimen were in ambient lab conditions at 19-23°C / 40-60% RH for at least 24 hours. ASTM Methods: D638 Type IV, 5mm/min. D790-B 1.3 mm/min; D256 Notched IZOD (Machine Notched) 6 mm x 12 mm; D2240 Type "D" (3, 5 seconds); D648 127 mm x 13 mm x 6.8 mm; D570 3.2 mm x 51 mm Disc 24hr@ 25°C; D792 solid 8 mm x 10 mm Disc; D5930 80 mm x 40 mm x 10 mm; E831 80 mm x 40 mm x 10 mm; D7867@ 25°C (77°F); D1475; D149 50 mm x 3 mm disc; D257 110 mm x 110 mm x 5 mm; D150 70 mm x 70 mm x 1.2 mm.

*The biological assessment has been performed based on the in vitro method according to ISO10993-23

Internal Data Sources:

[10] FOR90709 [11] FOR16921 [12] FOR16910 [16] FOR25879 [17] FOR25878 [18] FOR254522 [19] FOR25877 [20] FOR254521





IND403™ GENERAL PURPOSE BLACK



WORKFLOW

Validated workflows need to be followed to achieve properties as provided in the TDS. Examples of validated workflow steps are listed below. Users should defer to the most current workflow information for best results which can be found at <https://www.loctiteam.com/printer-validation-settings>

PRINTER SETTINGS

LOCTITE 3D IND403 BK is formulated to print optimally on industrial DLP printer. Read the safety data sheet carefully to get details about health and safety instructions. Recommended print parameters:

- Shake resin bottle well before usage
- Temperature: 20°C to 45°C
- Intensity: 3 mW/cm² to 7 mW/cm²

Settings: 385nm at 2 mW/cm ²	Measure	Method	Value
Layer Thickness	µm	Internal	100
Burn-in Region (s)	s	Internal	18
Transition Region (s):	s	Internal	9
Model Region (s):	s	Internal	7

Settings: 385nm at 5 mW/cm ²	Measure	Method	Value
E _C	mJ/cm ²	Internal	7.26 ^[21]
D _p	mm	Internal	0.12 ^[21]

Settings: 385nm at 5 mW/cm ²	Measure	Method	Exposure time
D _C = 50µm	s	Internal	2.3*
D _C = 100µm	s	Internal	3.40*

Test parameters:

*Exposure times are calculated without a safety factor

Internal Data Sources:
[21] GEN198946





IND403™ GENERAL PURPOSE BLACK



WORKFLOW

Validated workflows need to be followed to achieve properties as provided in the TDS. Examples of validated workflow steps are listed below. Users should defer to the most current workflow information for best results which can be found at <https://www.loctiteam.com/printer-validation-settings>

CLEANING

LOCTITE 3D IND403 BK requires post processing to achieve specified properties. Prior to post curing, support structures should be removed from the printed part, and the part should then be washed. Use compressed air to remove residual solvent from the surface of the material between intervals.

Post Process Step	Agent	Method	Duration	Intervals	Additional Info
Cleaning	IPA	Ultra sonic bath or manual cleaning	2 min	1 or 2	Allow parts to dry between intervals
Dry	n.a.	Compressed air	10 to 60 s	1 or 2	Air pressure (50psi)
Wait before post curing	n.a.	Ambient condition	60 min	1	Room temperature

POST CURING

LOCTITE 3D IND403 BK requires post curing to achieve specified properties. It is recommended that either an LED or wide spectrum lamp be used to post cure parts.

UV Curing Unit	UV Source	Intensity	Cure time per side	Additional Settings (Shelf, Output Energy)
Loctite CL36	405nm LED	80 mW/cm ² at 405 nm	20 min	100% top & side
Loctite UVALOC 1000	Mercury Arc Bulb (broad spectrum)	30 mW/cm ² at 365 nm	5 min	500 W, lowest shelf
Dymax 5000 EC Flood	Mercury Arc Bulb (broad spectrum)	150 mW/cm ² at 380 nm	2 min	400W, Shelf K

STORAGE

Store **LOCTITE 3D IND403 BK** in the unopened container in a dry location. Optimal Storage: 8°C to 30°C. Storage below 8°C or above 30°C can adversely affect product properties. Material removed from containers may be contaminated during use. For this reason, filter used resin with a 190µm mesh filter before placing it back into the proper storage container.





IND403™ GENERAL PURPOSE BLACK




AGEING AND ENVIRONMENTAL EFFECTS – HEAT AGEING

LOCTITE 3D IND403 BK was heat aged without load according to ASTM D3045. Test samples were exposed for a defined time at 50°C and conditioned for 24 hours at 22°C before mechanical testing. Control samples were stored at a constant 22°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D790 at standard lab conditions (22°C).


Values at '0 weeks' are non-aged samples stored at 22°C and tested after 24 hours of post-processing.

Based on temperature dependence of reaction rates a test time of 6 weeks at 50°C can be interpreted as approximately 12 months at ambient temperature.


Flexural Modulus after Heat Ageing at 50°C

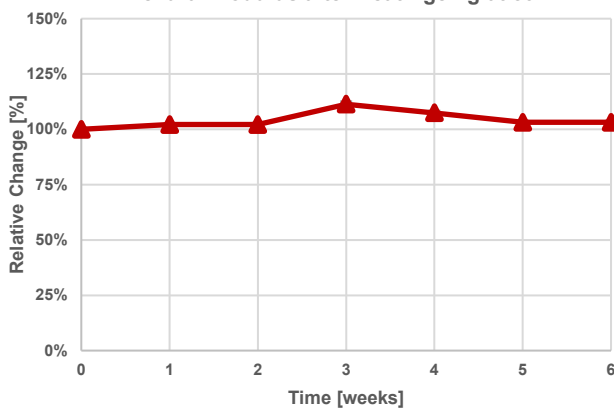

Flexural Elong. at Break after Heat Ageing at 50°C

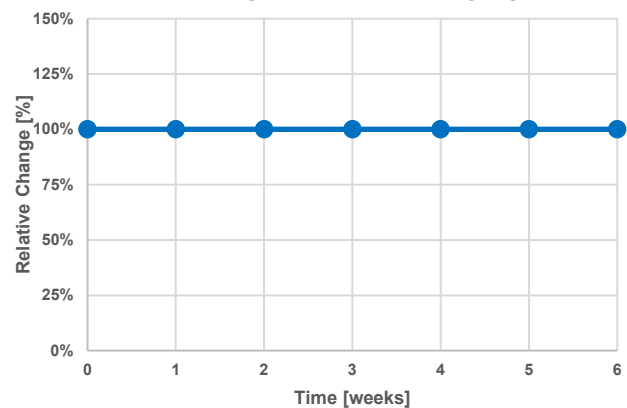

Flexural Stress at Break after Heat Ageing at 50°C

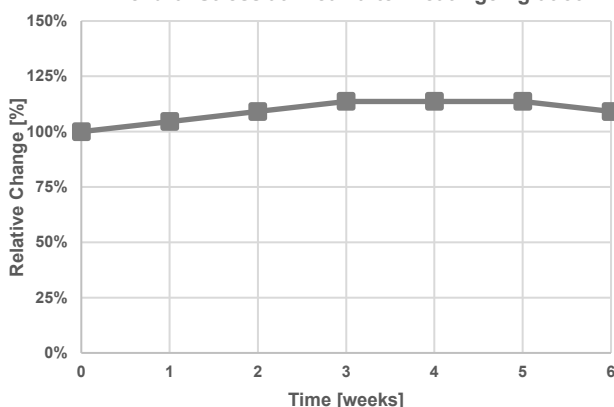

Test parameters:

ASTM D790: Test speed: 1.3 mm/min*, Test specimens: 85x12x3 mm, Flexural modulus measured at 0.1-1.0% (regression), 22°C

Internal Data Sources:

FOR103717, FOR103718





IND403™ GENERAL PURPOSE BLACK




AGEING AND ENVIRONMENTAL EFFECTS – HEAT AGEING

LOCTITE 3D IND403 BK was heat aged without load according to ASTM D3045. Test samples were exposed for a defined time at 50°C and conditioned for 24 hours at 22°C before mechanical testing. Control samples were stored at a constant 22°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D638 at standard lab conditions (22°C).


Values at '0 weeks' are non-aged samples stored at 22°C and tested after 24 hours of post-processing.

Based on temperature dependence of reaction rates a test time of 6 weeks at 50°C can be interpreted as approximately 12 months at ambient temperature.


Young's Modulus after Heat Ageing at 50°C

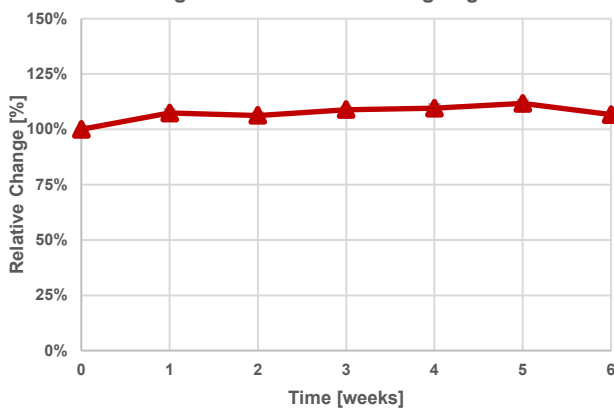


Elongation at Break after Heat Ageing at 50°C

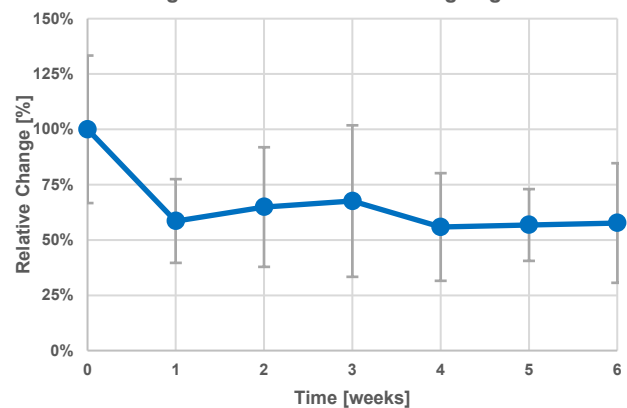

Stress at Break after Heat Ageing at 50°C

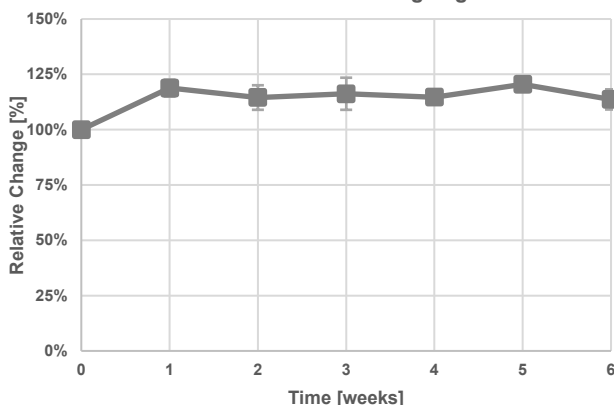

Stress at Yield after Heat Ageing at 50°C

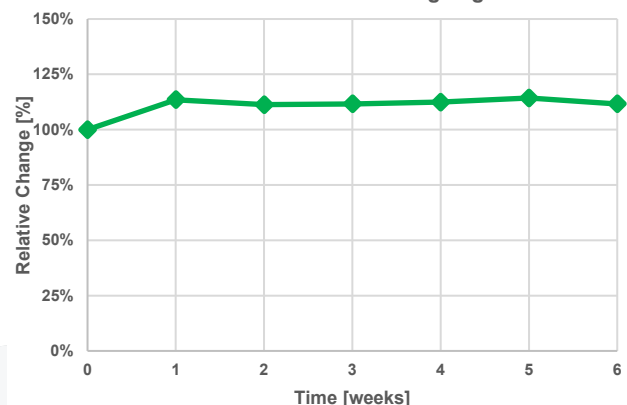

Test parameters:
ASTM D638: Type IV, Pull speed: 5 mm/min, Young's modulus measured at 0.1-1.0% (regression), 22°C

Internal Data Sources:
[FOR351771](#), [FOR351775](#)



LOCTITE®

IND403™
GENERAL PURPOSE
BLACK




AGEING AND ENVIRONMENTAL EFFECTS – ACCELERATED WEATHERING (UV AGEING)

LOCTITE 3D IND403 BK has been tested after accelerated outdoor weathering according to ASTM D4329 (Cycle A). Test samples were exposed to defined conditions of heat, water condensation and UV light. Exposed samples were conditioned for 24 hours at 22°C before mechanical testing. Control samples were stored at a constant 22°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D790 at standard lab conditions (22°C).


Values at '0 weeks' are non-aged samples stored at 22°C and tested after 24 hours of post-processing.

Please note, accelerated weathering testing can never fully represent real outdoor conditions and complexity. It is therefore recommended to conduct additional (outdoor) testing relevant for your specific application needs.


Flexural Modulus after UV Ageing

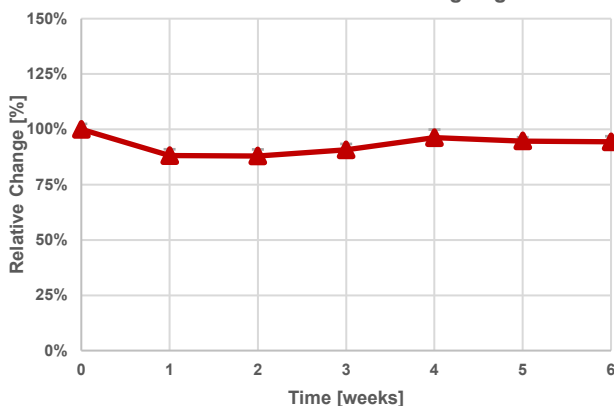

Flexural Elongation at Break after UV Ageing

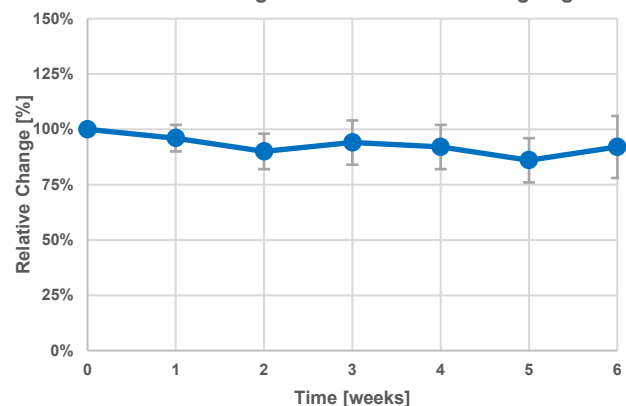

Flexural Stress at Break after UV Ageing

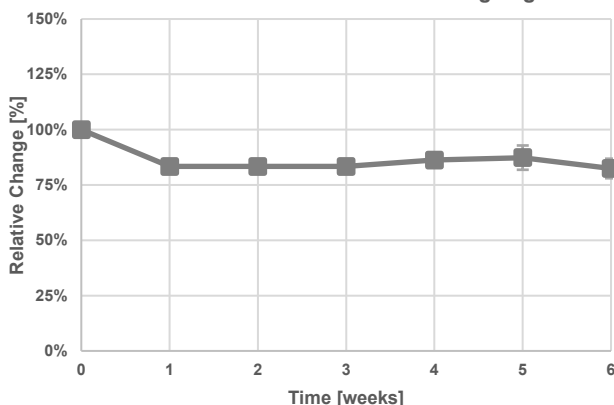

Test parameters:

ASTM D790: Test speed: 1.3 mm/min, Test specimens: 85x12x3 mm, Flexural modulus measured at 0.1-1.0% (regression), 22°C

ASTM D4329: Cycle A for general applications, QUV/se, UVA 340 nm, 0.89 W/m²·nm, 8 hours UV light at 60°C followed by 4 hours at 50°C condensation in the dark. To reduce any sample warpage during test time samples were placed in tailor-made holders without any fixation clamps or mechanical load. Exposed samples were always removed from QUV before next condensation cycle to avoid samples that are soaked excessively with water before testing.

Internal Data Sources:

FOR148177, FOR148236



LOCTITE®

IND403™
GENERAL PURPOSE
BLACK







AGEING AND ENVIRONMENTAL EFFECTS – ACCELERATED WEATHERING (UV AGEING)

LOCTITE 3D IND403 BK has been tested after accelerated outdoor weathering according to ASTM D4329 (Cycle A). Test samples were exposed to defined conditions of heat, water condensation and UV light. Exposed samples were conditioned for 24 hours at 22°C before mechanical testing. Control samples were stored at a constant 22°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D638 at standard lab conditions (22°C).

Values at '0 weeks' are non-aged samples stored at 22°C and tested after 24 hours of post-processing.

Please note, accelerated weathering testing can never fully represent real outdoor conditions and complexity. It is therefore recommended to conduct additional (outdoor) testing relevant for your specific application needs.

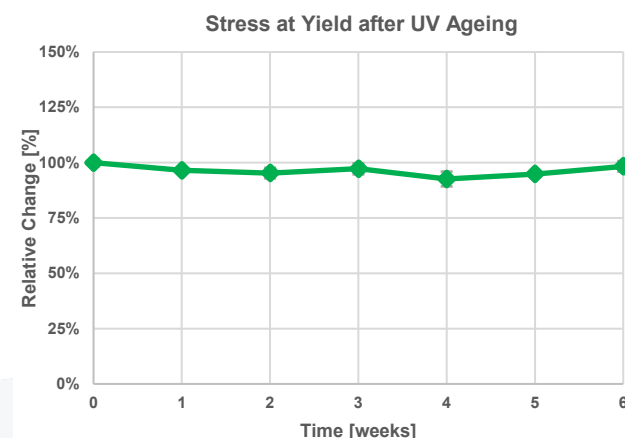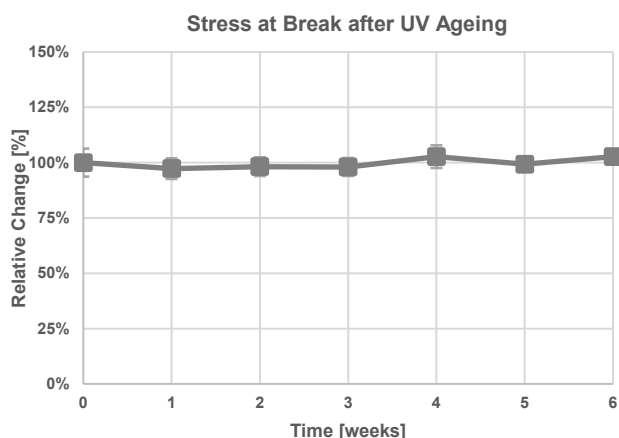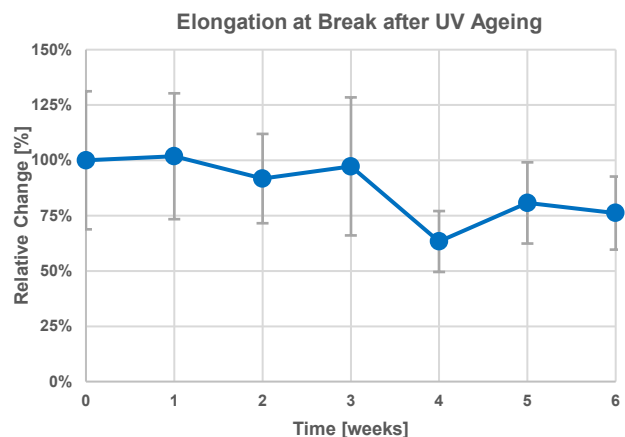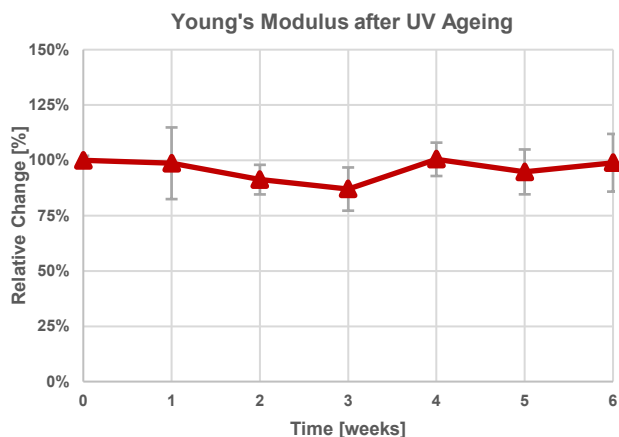

Test parameters:

ASTM D638: Type IV, Pull speed: 5 mm/min, Young's modulus measured at 0.1-1% (regression), 22 °C
ASTM D4329: Cycle A for general applications, QUV/se, UVA 340 nm, 0.89 W/m²·nm, 8 hours UV light at 60°C followed by 4 hours at 50°C condensation in the dark. To reduce any sample warpage during test time samples were placed in tailor-made holders without any fixation clamps or mechanical load. Exposed samples were always removed from QUV before next condensation cycle to avoid samples that are soaked excessively with water before testing.

Internal Data Sources:

FOR461136, FOR431134





IND403™ GENERAL PURPOSE BLACK







AGEING AND ENVIRONMENTAL EFFECTS – CLIMATE CYCLING TEST (PV1200)

LOCTITE 3D IND403 BK was tested in an environmental climate cycling test according to PV1200 specification. This specification was developed by Volkswagen AG to evaluate material durability and cycles between -40°C (4 hours) and 80°C (4 hours at 80 % rel. humidity) during a repeating 12-hour cycle. Test samples were exposed to this temperature cycle for a total duration of 7 weeks (100 cycles).

Before mechanical testing samples were conditioned for 24 hours at 22°C. Control samples were stored at a constant 22°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D638 at standard lab conditions (22°C).

Values at '0 weeks' are non-aged samples stored at 22°C and tested after 24 hours of post-processing.

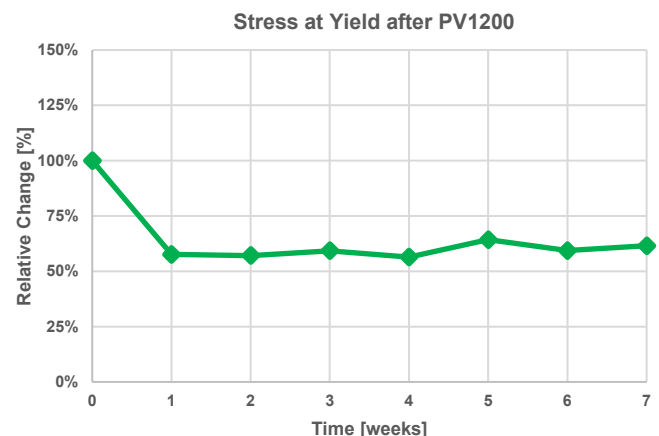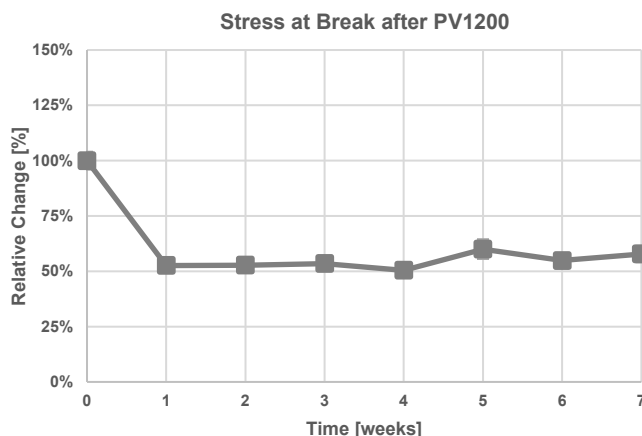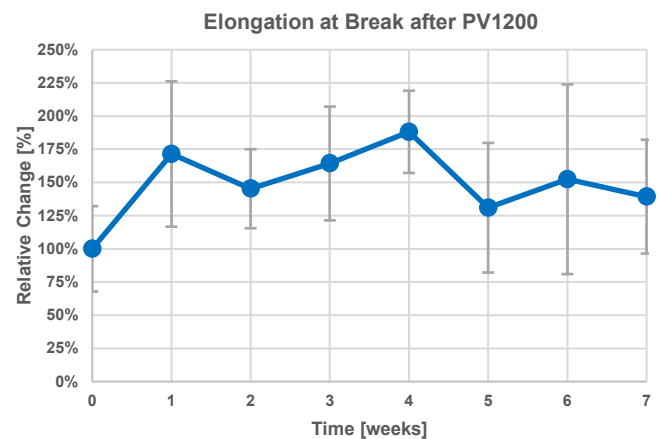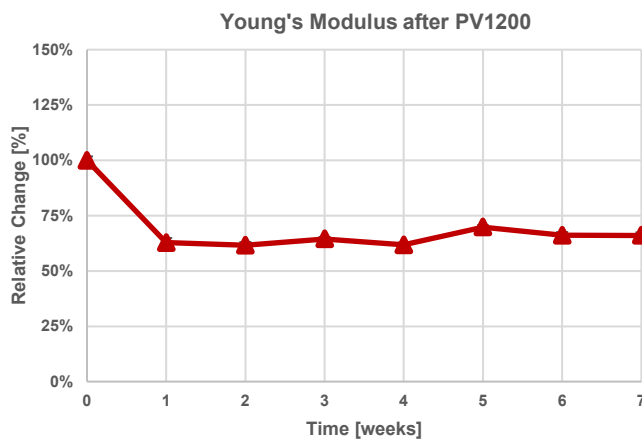

Test parameters:

ASTM D638: Type IV, Pull speed: 50 mm/min, Young's modulus measured at 0.1-1.0% (regression), 22°C

PV1200: Samples were removed from climate chamber during heating phase (Cycle time: 240-300 minutes) and then conditioned for 24 hours at 22°C. 1 Test cycle is equal to 12 hours of test time. "7 weeks" of test time represent 100 test cycles or 1200 hours of test time.

Internal Data Sources:

FOR589061






IND403™ GENERAL PURPOSE BLACK




THERMAL INFLUENCE ON MECHANICAL PROPERTIES

LOCTITE 3D IND403 BK has been tested according to ASTM D638 at varied environmental temperatures, from -40°C to 100°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D638. Before each test series samples were conditioned for 60 minutes at the specific test temperature.


Young's Modulus at -40°C to 100 °C

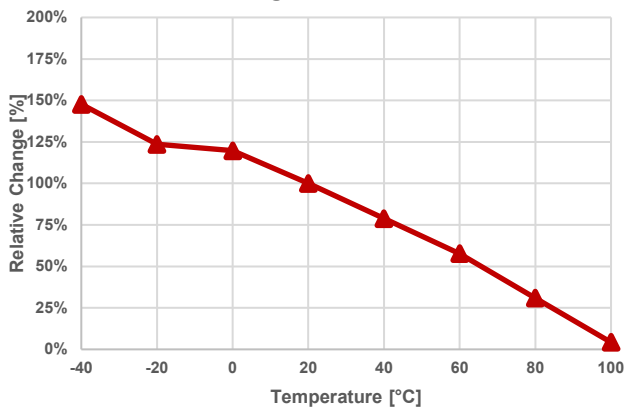


Elongation at Break at -40°C to 100 °C

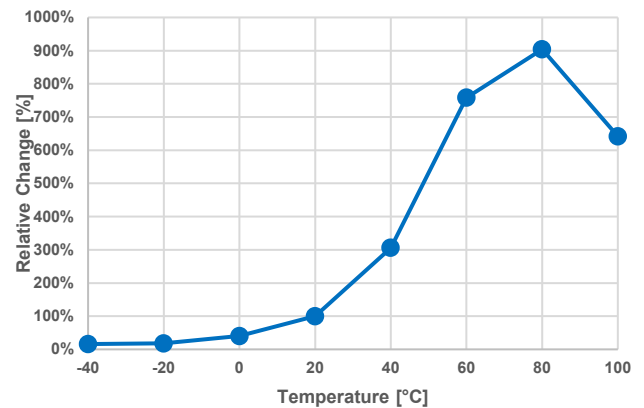

Stress at Break at -40°C to 100 °C

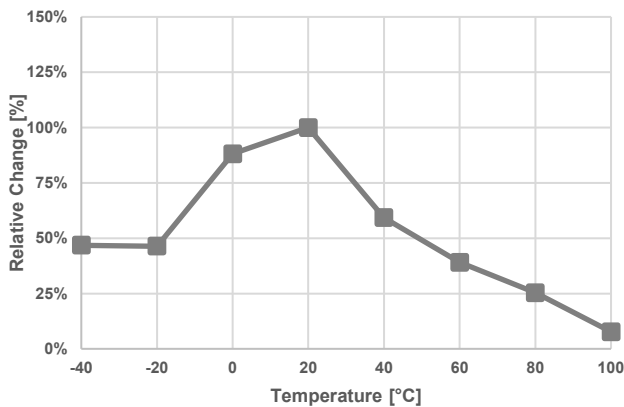

Stress at Yield at -40°C to 100 °C

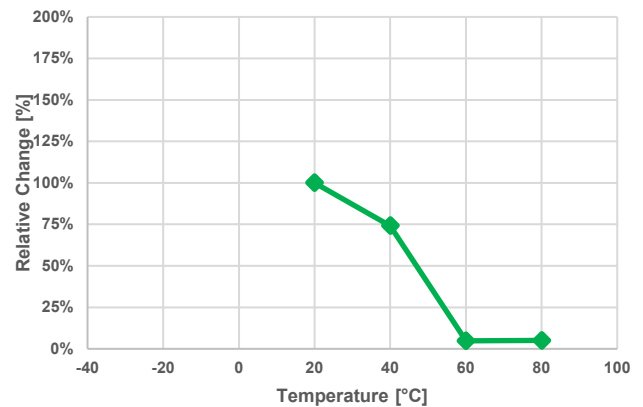

Test parameters:
ASTM D638, Type IV, Pull speed: 5 mm/min, Young's modulus measured at 0.1-1% (regression),

Internal Data Sources:
[FOR101977](#)









IND403™ GENERAL PURPOSE BLACK



AGEING AND ENVIRONMENTAL EFFECTS – CHEMICAL RESISTANCE INDUSTRIAL

LOCTITE 3D IND403 BK has been tested after chemical ageing according to ASTM D543. The influence of chemicals was tested by measuring mechanical properties after different test times (Immersion test for 24 and 168 hours). Exposed samples were stored in containers and fully immersed in different chemicals. Samples were stirred every 24 hours using a shaker. After removal, exposed samples were washed and conditioned for 24 hours at 22°C before mechanical testing. All samples were printed using a validated workflow. Mechanical testing was conducted according to ASTM D638 at standard lab conditions (22°C). The 100% value represents the initial weight 24 hours after post-processing.

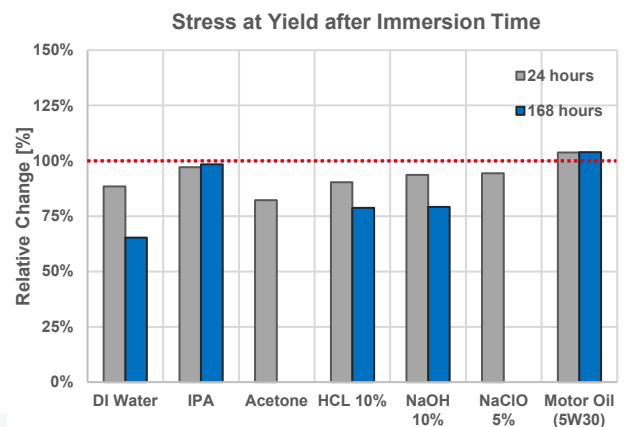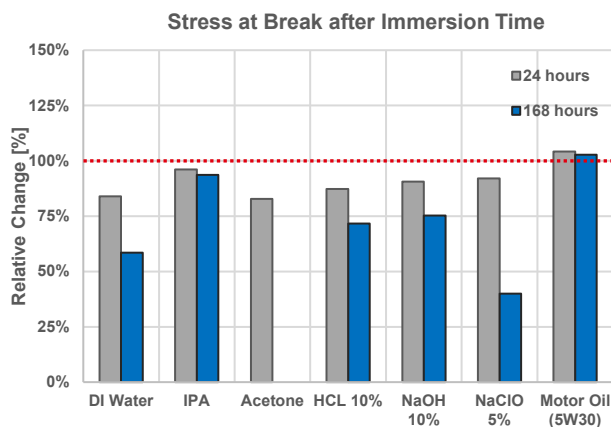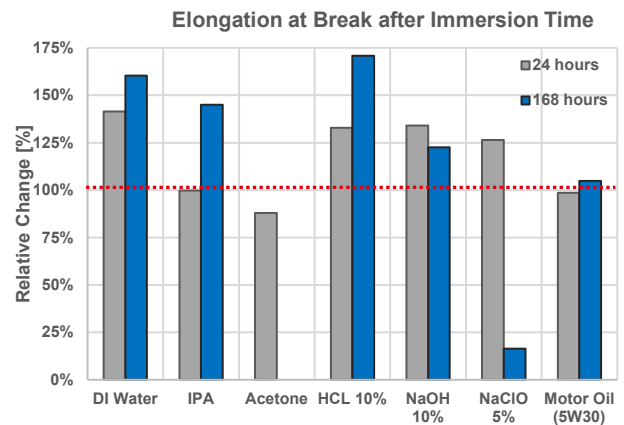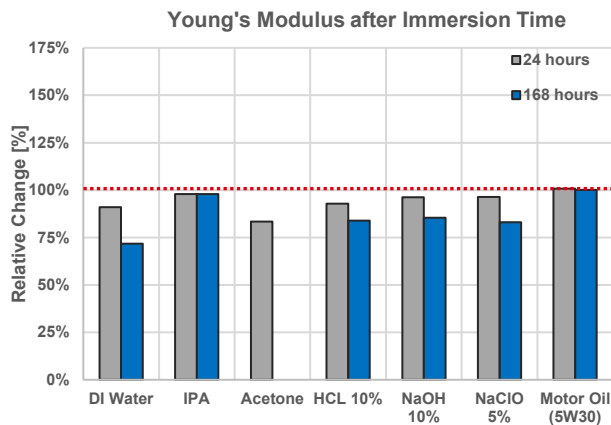

Test parameters:

ASTM D638: Type IV, Pull speed: 5 mm/min, 22°C

ASTM D543: Samples immersed in different chemicals were stored at 22°C. Samples immersed in Motor Oil were stored at 50°C

Comment: The samples after 168h after the immersion in Acetone were not possible to test, therefore there is no value for this immersion time

Internal Data Sources:

FOR282116, FOR282127, FOR282131, FOR282134, FOR288317, FOR288318, FOR288320









IND403™ GENERAL PURPOSE BLACK



AGEING AND ENVIRONMENTAL EFFECTS – CHEMICAL RESISTANCE AUTOMOTIVE

LOCTITE 3D IND403 BK has been tested after chemical ageing according to ASTM D543. The influence of chemicals was tested by measuring mechanical properties after different test times (Immersion test for 24 and 168 hours). Exposed samples were stored in containers and fully immersed in different chemicals. Samples were stirred every 24 hours using a shaker. After removal, exposed samples were washed and conditioned for 24 hours at 22°C before mechanical testing. All samples were printed using a validated workflow. Mechanical testing was conducted according to ASTM D638 at standard lab conditions (22°C). The 100% value represents the initial weight 24 hours after post-processing.

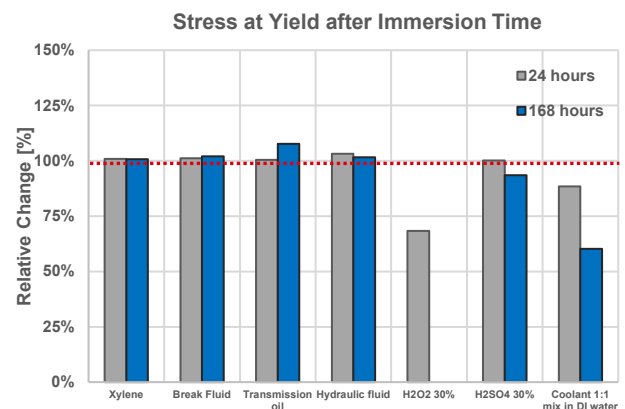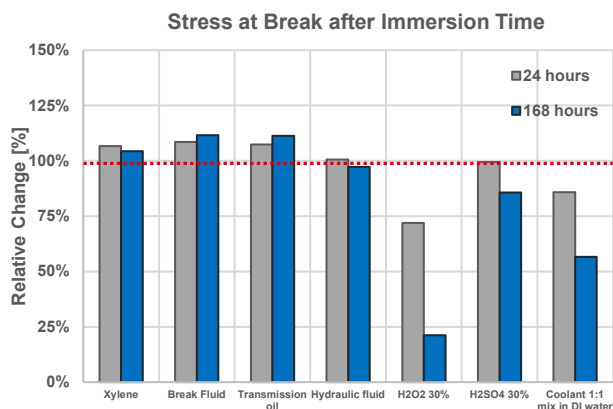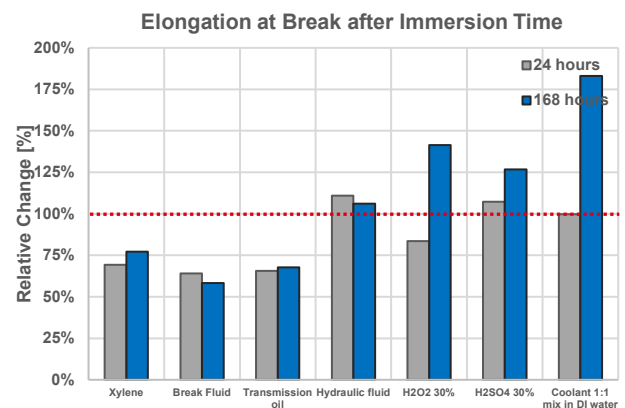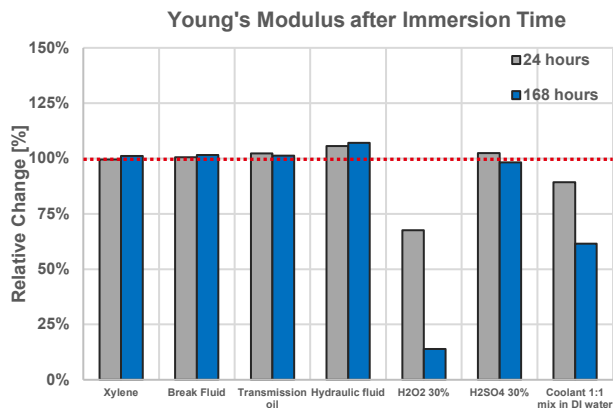

Test parameters:

ASTM D638: Type IV, Pull speed: 5 mm/min, Young's modulus measured at 0.1-1.0% (regression), 22°C. ASTM D543: Samples immersed in different chemicals were stored at 22°C. Samples immersed in Transmission oil and Coolant mix 1:1 were stored at 50°C. Properties of media used: pH(H₂SO₄ 30%) = 0; pH(H₂O₂ 30%) = 5; pH (NaCl solution 0.9%) = 5. Viscosity: Hydraulic fluid = 3000 mPas at 40°C; Transmission oil = 8200 mPas at 40°C; Minimum temperature of coolant mix 1:1 = -40°C. Comment: The samples after 168 h after the immersion in Acetone were not possible to test, therefore there is no value for this immersion time.

Internal Data Sources:

FOR815405, FOR829359, FOR829358, FOR829353, FOR815409, FOR815410, FOR815401







IND403™ GENERAL PURPOSE BLACK



AGEING AND ENVIRONMENTAL EFFECTS – CHEMICAL RESISTANCE MASS SOAK

LOCTITE 3D IND403 BK has been tested after chemical ageing according to ASTM D543. The influence of chemicals was tested by measuring the mass change after different test times (Immersion test for 24 and 168 hours). Exposed samples were stored in containers and fully immersed in different chemicals. Samples were stirred every 24 hours using a shaker. After removal exposed samples were washed, dried and immediately weighed. All samples were printed using a validated workflow.

The 100% value represents the initial weight 24 hours after post-processing.

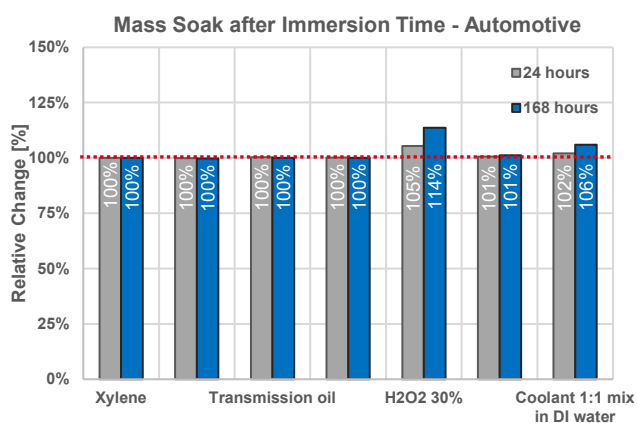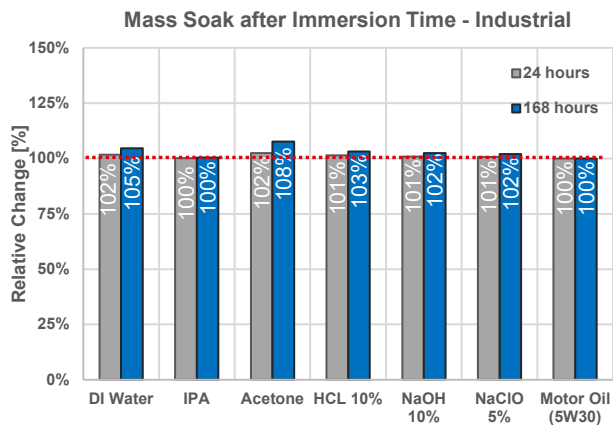

Test parameters:

ASTM D543: Samples immersed in different chemicals were stored at 22°C. Samples immersed in Motor Oil, Transmission Oil and Coolant mix 1:1 were stored at 50°C.
Properties of media used: pH(HCl, 10%) = 1; pH(NaOH 10%) = 14; pH(NaClO 5%) = 13; pH(H₂SO₄ 30%) = 0; pH(H₂O₂ 30%) = 5; pH (NaCl solution 0.9%) = 5
Viscosity: Hydraulic fluid = 3000 mPas at 40°C; Transmission oil = 8200 mPas at 40°C;
Minimum temperature for coolant mix 1:1 = -40°C

Internal Data Sources:

FOR282136, FOR282146, FOR282174, FOR288321, FOR288322, FOR288323, FOR815405, FOR829359, FOR829358, FOR829353, FOR815409, FOR815410, FOR815401



LOCTITE®

IND403™
GENERAL PURPOSE
BLACK




AGEING AND ENVIRONMENTAL EFFECTS – SALT SPRAY EXPOSURE

LOCTITE 3D IND403 BK was aged according to ASTM B117-19. During the test samples were exposed to salt spray at 35°C. After removal from the test chamber, exposed samples were dried, inspected, cleaned using water and wiped dry. Before mechanical testing, samples were conditioned for 24 hours at 22°C. All samples were printed in the same print job using a validated workflow. Mechanical testing was conducted according to ASTM D638 at standard lab conditions (22°C).


Values at '0 weeks' are non-aged samples stored at 22°C and tested after 24 hours of post-processing.

Please note, accelerated weathering testing can never fully represent real outdoor conditions and complexity. It is therefore recommended to conduct additional (outdoor) testing relevant for your specific application needs.


Young's Modulus after Salt Spray at 35°C

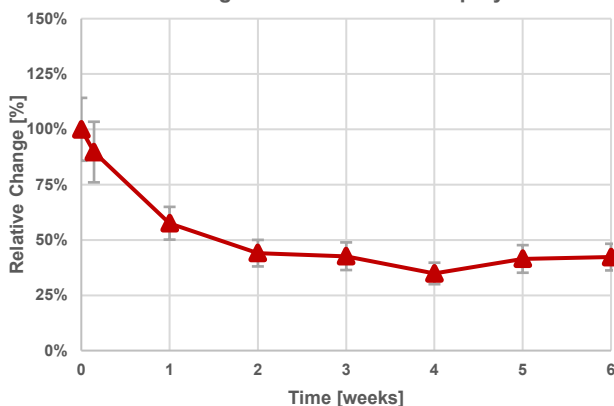


Elongation at Break after Salt Spray at 35°C

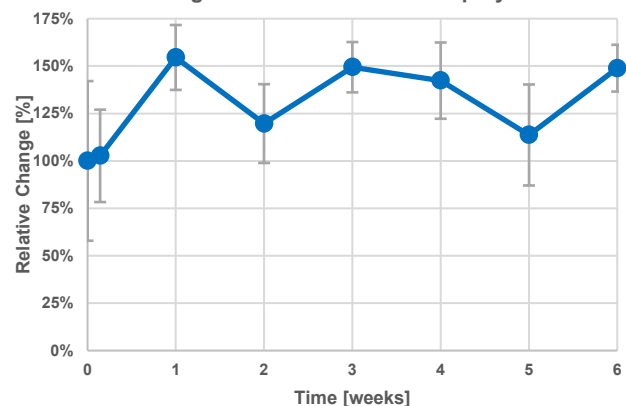

Stress at Break after Salt Spray at 35°C

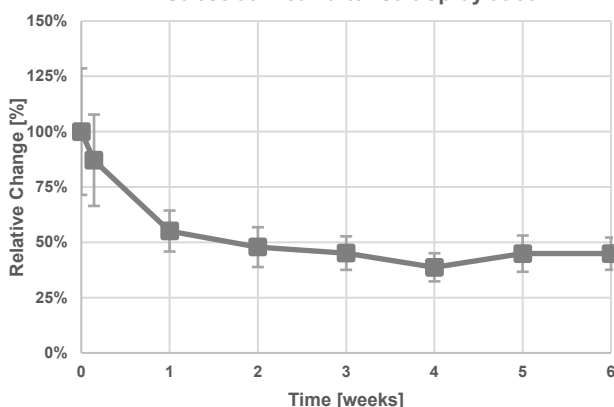

Stress at Yield after Salt Spray at 35°C

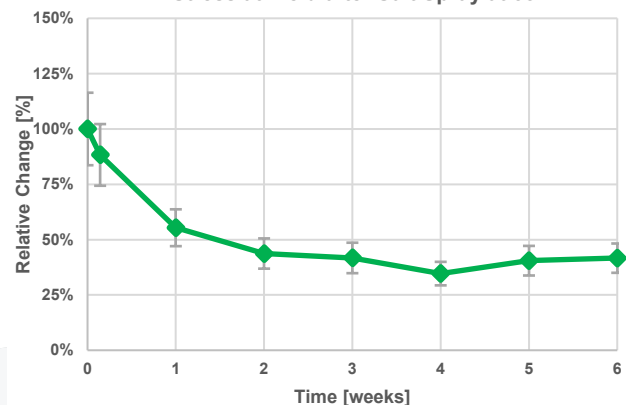

Test parameters:

ASTM B117-19: pH = 6.1; Fog collection = 1.3 ml/h

ASTM D638: Type IV, Pull speed: 5 mm/min, Young's modulus measured at 0.1-1.0% (regression), 22°C

Internal Data Sources:

FOR635366, FOR635320



LOCTITE®

IND403™
GENERAL PURPOSE
BLACK




AGEING AND ENVIRONMENTAL EFFECTS – SALT SPRAY EXPOSURE

LOCTITE 3D IND403 BK has been tested after salt spray exposure according to ASTM B117-19. All samples were printed in the same print job using a validated workflow. After removal from the salt spray environment, exposed samples were dried, inspected, cleaned using water, wiped dry and immediately weighed.

The influence of the salt spray was measured by mass change after different exposure times. Samples were weighed after 24 hours and 1 to 6 weeks.

The 100% value represents the initial weight 24 hours after post-processing.

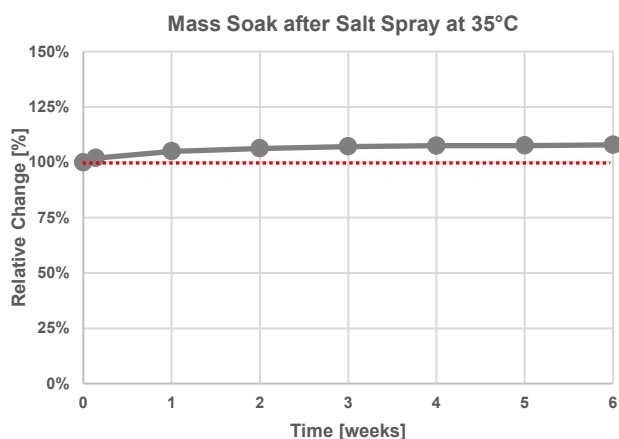

Test parameters:
ASTM B117-19: pH = 6.1; Fog collection = 1.3 ml/h

Internal Data Sources:
[FOR635320](#)





IND403™

GENERAL PURPOSE
NATURAL



PROPERTIES

Mechanical Properties	Measure	Method	Green	Post Processed
Young's Modulus	MPa	ASTM D638	1620 – 2070 [3,4]	2950 – 3200 [1,2]
Tensile Stress at Yield	MPa	ASTM D638	40 – 50 [4,3]	-
Elongation at Yield	MPa	ASTM D638	3.9 – 4.6 [3,4]	-
Tensile Stress at Break	MPa	ASTM D638	33 – 40 [3,4]	61 – 74 [1,2]
Elongation at Break	%	ASTM D638	6.2 – 16.8 [3,4]	2 – 11 [1,2]
Flexural Modulus	MPa	ASTM D790	1180 – 1320 [5,6]	2455 – 3220 [7,8]
Flexural Stress at Break	MPa	ASTM D790	-	-
Flexural Elongation at Break	%	ASTM D790	> 5 [5,6]	> 5 [7,8]
IZOD Impact (Notched)	J/m	ASTM D256	-	23 – 32 [9]
Shore Hardness (3s)	D	ASTM D2240	-	83 – 84 [14]
Other Properties				
HDT at 0.455 MPa	°C	ASTM D648	-	67 – 102 [17,18]
HDT at 1.82 MPa	°C	ASTM D648	-	52 – 87 [17,18]
Water absorption (24h)	%	ASTM D570	-	0.79 – 1.19 [24,16]
Water absorption (48h)	%	ASTM D570	-	1.10 – 1.20 [24]
Water absorption (72h)	%	ASTM D570	-	1.34 – 2.17 [16,24]
Water absorption (168h)	%	ASTM D570	-	2.00 – 2.93 [16,24]
Solid Density	g/cm ³	ASTM D792	-	1.18 – 1.20 [15]
Thermal Conductivity	mW/(m·K)	ASTM D5930	-	201 – 202 [23]
Heat Capacity	J/(g·K)	ASTM D5930	-	1.40 – 1.50 [23]

Test parameters:

All specimen are printed unless otherwise noted. All specimen were in ambient lab conditions at 19-23°C / 40-60% RH for at least 24 hours. ASTM Methods: D638 Type IV, 5mm/min; D790-B 1.3 mm/min; D256 Notched IZOD (Machine Notched) 6 mm x 12 mm; D2240 Type "D" (3, 5 seconds); D648 127 mm x 13 mm x 6.8 mm; D570 3.2 mm x 51 mm Disc 24hr@ 25°C; D792 solid 8 mm x 10 mm Disc; D5930 80 mm x 40 mm x 10 mm; E831 80 mm x 40 mm x 10 mm; D7867@ 25°C (77°F); D1475; D149 50 mm x 3 mm disc; D257 110 mm x 110 mm x 5 mm; D150 70 mm x 70 mm x 1.2 mm.

*The biological assessment has been performed based on the in vitro method according to ISO10993-23

Internal Data Sources:

[1] FOR394947, [2] FOR27471, [3] FOR389878, [4] FOR394939, [5] FOR33226, [6] FOR24159, [7] FOR24166, [8] FOR26649 [9] FOR24161, [14] FOR485264, [15] FOR484669, [16] FOR484661, [17] FOR30840, [18] FOR24133, [19] FOR518589, [23] FOR27485, [24] FOR610607





IND403™

GENERAL PURPOSE
NATURAL



PROPERTIES

Mechanical Properties	Measure	Method	Green	Post Processed
CTE (< T _{G1})	μm/(m·K)	ASTM E831	-	73 – 87 [19]
CTE (> T _{G2})	μm/(m·K)	ASTM E831	-	113 – 130 [19]
T _{G1} (Primary)	°C	ASTM E831	-	52 – 54 [19]
T _{G2} (Secondary)	°C	ASTM E831	-	-
Liquid Properties				
Viscosity at 25°C (77°F)	cP	ASTM D7867	-	136 – 142 [11,12]
Liquid Density	g/cm ³	ASTM D1475	-	1.02 [13]
Electrical Properties				
Dielectric Strength	kV/mm	ASTM D149	-	27 – 28 [20]
Volume Resistivity	Ω·cm	ASTM D257	-	2.1·10 ¹⁵ [21]
Surface Resistivity	Ω	ASTM D257	-	7.8·10 ¹⁴ [21]
AC Relative Permittivity (Dielectric Constant)				
at 50 Hz	none	ASTM D150	-	3.5 [22]
at 1 kHz	none	ASTM D150	-	3.4 [22]
at 1 MHz	none	ASTM D150	-	3.2 [22]
AC Loss Characteristic (Dissipation Factor)				
at 50 Hz	none	ASTM D150	-	0.12 [22]
at 1 kHz	none	ASTM D150	-	0.08 [22]
at 1 MHz	none	ASTM D150	-	0.08 [22]

Test parameters:

All specimen are printed unless otherwise noted. All specimen were in ambient lab conditions at 19-23°C / 40-60% RH for at least 24 hours. ASTM Methods: D638 Type IV, 5mm/min; D790-B 1.3 mm/min; D256 Notched IZOD (Machine Notched) 6 mm x 12 mm; D2240 Type "D" (3, 5 seconds); D648 127 mm x 13 mm x 6.8 mm; D570 3.2 mm x 51 mm Disc 24hr@ 25°C; D792 solid 8 mm x 10 mm Disc; D5930 80 mm x 40 mm x 10 mm; E831 80 mm x 40 mm x 10 mm; D7867@ 25°C (77°F); D1475; D149 50 mm x 3 mm disc; D257 110 mm x 110 mm x 5 mm; D150 70 mm x 70 mm x 1.2 mm.

*The biological assessment has been performed based on the in vitro method according to ISO10993-23

Internal Data Sources:

[11] FOR24255, [12] FOR469694, [13] FOR24158, [19] FOR518589, [20] FOR530827, [21] FOR530835, [22] FOR530814





IND403™ GENERAL PURPOSE NATURAL



WORKFLOW

Validated workflows need to be followed to achieve properties as provided in the TDS. Examples of validated workflow steps are listed below. Users should defer to the most current workflow information for best results which can be found at <https://www.loctiteam.com/printer-validation-settings>

PRINTER SETTINGS

LOCTITE 3D IND403 NAT is formulated to print optimally on industrial DLP printer. Read the safety data sheet carefully to get details about health and safety instructions. Recommended print parameters:

- Shake resin bottle well before usage
- Temperature: 20°C to 45°C
- Intensity: 3 mW/cm² to 7 mW/cm²

Settings: 385nm at 5 mW/cm ²	Measure	Method	Value
Layer Thickness (μm):	μm	Internal	100
Burn-in Region (s)	s	Internal	40
Transition Region (s):	s	Internal	18
Model Region (s):	s	Internal	4.5

Settings: 385nm at 5 mW/cm ²	Measure	Method	Value
E _C	mJ/cm ²	Internal	6.29 ^[25]
D _p	mm	Internal	0.15 ^[25]

Settings: 385nm at 5 mW/cm ²	Measure	Method	Exposure time
D _C = 50μm	s	Internal	1.6 ^{*[25]}
D _C = 100μm	s	Internal	2.1 ^{*[25]}

Test parameters:

*Exposure times are calculated without a safety factor

Internal Data Sources:

[25] FOR26626





IND403™ GENERAL PURPOSE NATURAL



WORKFLOW

Validated workflows need to be followed to achieve properties as provided in the TDS. Examples of validated workflow steps are listed below. Users should defer to the most current workflow information for best results which can be found at <https://www.loctiteam.com/printer-validation-settings>

CLEANING

LOCTITE 3D IND403 NAT requires post processing to achieve specified properties. Prior to post curing, support structures should be removed from the printed part, and the part should then be washed. Use compressed air to remove residual solvent from the surface of the material between intervals.

Post Process Step	Agent	Method	Duration	Intervals	Additional Info
Cleaning	IPA	Ultra sonic bath	2 min	2	Dry after each interval
Dry	n.a.	Compressed air	10 to 60 s	2	Air pressure (50psi)
Wait before post curing	n.a.	Ambient condition	60 min	1	Room temperature

POST CURING

LOCTITE 3D IND403 NAT requires post curing to achieve specified properties. It is recommended that either an LED or wide spectrum lamp be used to post cure parts.

UV Curing Unit	UV Source	Intensity	Cure time per side	Additional Settings (Shelf, Output Energy)
Loctite CL36	405nm LED	80 mW/cm ² at 405 nm	20 min	100% top & side
Loctite UVALOC 1000	Mercury Arc Bulb (broad spectrum)	30 mW/cm ² at 365 nm	5 min	500 W, lowest shelf
Dymax 5000 EC Flood	Mercury Arc Bulb (broad spectrum)	150 mW/cm ² at 380 nm	10 min	400W, Shelf K

STORAGE

Store **LOCTITE 3D IND403 NAT** in the unopened container in a dry location. Optimal Storage: 8°C to 30°C. Storage below 8°C or above 30°C can adversely affect product properties. Material removed from containers may be contaminated during use. For this reason, filter used resin with a 190µm mesh filter before placing it back into the proper storage container.



LOCTITE®

IND403™
GENERAL PURPOSE



NOTE

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on our knowledge and experience of the product as at the date of this TDS. The product can have a variety of different applications as well as differing application and working conditions in your environment that are beyond our control. Henkel is, therefore, not liable for the suitability of our product for the production processes and conditions in respect of which you use them, as well as the intended applications and results. We strongly recommend that you carry out your own prior trials to confirm such suitability of our product.

Any liability in respect of the information in the Technical Data Sheet or any other written or oral recommendation(s) regarding the concerned product is excluded, except if otherwise explicitly agreed and except in relation to death or personal injury caused by our negligence and any liability under any applicable mandatory product liability law.

In case products are delivered by Henkel Belgium NV, Henkel Electronic Materials NV, Henkel Nederland BV, Henkel Technologies France SAS and Henkel France SA please additionally note the following:

In case Henkel would be nevertheless held liable, on whatever legal ground, Henkel's liability will in no event exceed the amount of the concerned delivery.

In case products are delivered by Henkel Colombiana, S.A.S. the following disclaimer is applicable:

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on our knowledge and experience of the product as at the date of this TDS. Henkel is not liable for the suitability of our product for the production processes and conditions in respect of which you use them, as well as the intended applications and results. We strongly recommend that you carry out your own prior trials to confirm such suitability of our product.

Any liability in respect of the information in the Technical Data Sheet or any other written or oral recommendation(s) regarding the concerned product is excluded, except if otherwise explicitly agreed and except in relation to death or personal injury caused by our negligence and any liability under any applicable mandatory product liability law.

In case products are delivered by Henkel Corporation, Resin Technology Group, Inc., or Henkel Canada, Inc. the following disclaimer is applicable:

The data contained herein are furnished for information only and are believed to be reliable. We cannot assume responsibility for the results obtained by others over whose methods we have no control. It is the user's responsibility to determine suitability for the user's purpose of any production methods mentioned herein and to adopt such precautions as may be advisable for the protection of property and of persons against any hazards that may be involved in the handling and use thereof. In light of the foregoing, Henkel Corporation specifically disclaims all warranties expressed or implied, including warranties of merchantability or fitness for a particular purpose, arising from sale or use of **Henkel Corporation's products. Henkel Corporation specifically disclaims any liability for consequential or incidental damages of any kind, including lost profits.** The discussion herein of various processes or compositions is not to be interpreted as representation that they are free from domination of patents owned by others or as a license under any Henkel Corporation patents that may cover such processes or compositions. We recommend that each prospective user test his proposed application before repetitive use, using this data as a guide. This product may be covered by one or more United States or foreign patents or patent applications.

Trademark Usage

Except as otherwise noted, all trademarks in this document are trademarks of Henkel Corporation in the U.S. and elsewhere. ® denotes a trademark registered in the U.S. Patent and Trademark Office.



LOCTITE®



FIND OUT MORE AT
LOCTITEAM.COM

LOCTITE®
Henkel Corporation
loctite3d@henkel.com



Version 2025/07/22